

承 认 书

SPECIFICATION FOR APPROVAL

客户名称:

CUSTOMER: _____

产品名称 多层片式瓷介电容器

PARTNAME: Multilayer Chip Ceramic Capacitor

产品规格

通用系列

SPECIFICATION: _____


承认书编号

APPROVAL SHEET NO.: DRAAW108J/0-2021

发出日期

ISSUED DATE: _____

制造 MANUFACTURER			客户 CUSTOMER		
批准 APPROVED	审核 CHECKED	经办 PREPARED	批准 APPROVED	审核 CHECKED	经办 PREPARED
梁俊	翟艳明	张国信			

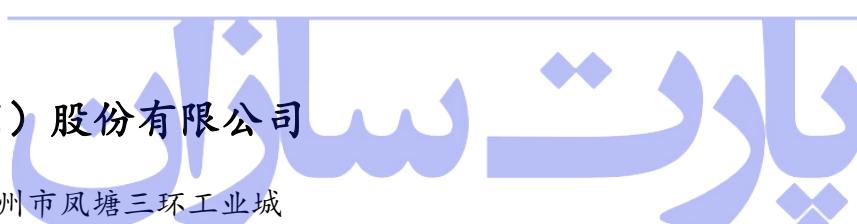
潮州三环（集团）股份有限公司

地址：中国广东省潮州市凤塘三环工业城

电话：86-768-6855932

传真：86-768-6855921

网址：HTTP://WWW.CCTC.CC

PARTSAZAN Co.
@PARTSAZAN_LED
02166732484

传真(Fax): (768) 6855928, 6855921

Website: http://www.cctc.cc

电话(Tel): 86-768-6855949, 685923

 E-mail: market@china-threecircle.com



潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.
地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646
ADD : San Huan Industrial District, Feng Tang Chao Zhou, GuangDong, China

文件编号	DRAAW108J/0-2021			页数	39
文件名称	多层片式陶瓷电容器(产品承认书)			制订日期	2012.01
版数	制定、修订日期	页数	制定、修订内容		登记者
B/0	2012-01-11	38	新制定		方千军
B/1	2012-08-11	36	增加 2225、1808 尺寸的载带尺寸		王彬彬
C/0	2013-01-10	39	换版		王彬彬
D/0	2014-01-06	39	更新 SGS 报告		王彬彬
E/0	2014-05-06	44	换版		张国信
F/0	2015-02-10	44	换版		张国信
G/0	2016-05-15	44	换版		张国信
H/0	2017-07-01	44	换版		张国信
I/0	2020-02-12	44	换版		张国信
J/0	2021-01-07	39	增加 0201 尺寸及 X6S\X7T 材质， 删除 1210 尺寸以上规格		张国信

پارتسازان

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel) : 86-768-6855949 , 685923

E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928 , 68559214

Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATIONFOR APPROVAL	DRAAW108J/0-2021

目录

1. 电容器及介质分类.....	3
2. 产品结构.....	4
3. 产品规格型号命名规则.....	5
4. 产品容量范围.....	6
0201 (0603) 尺寸.....	7
0402 (1005) 尺寸.....	7
0603 (1608) 尺寸.....	9
0805 (2012) 尺寸.....	11
1206 (3216) 尺寸.....	13
1210 (3225) 尺寸.....	15
5. 产品尺寸.....	17
6. 技术要求和测试条件.....	18
7. 产品包装.....	29
8. MLCC 使用注意事项.....	34



潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646
ADD : San Huan Industrial District ,Feng Tang Chao Zhou,GuangDong,China

产品标准书 SPECIFICATION FOR APPROVAL	编 号 Document No. DRAAW108J/0-2021
--	---

1. 电容器及介质分类 Types of Capacitor and Dielectric Material

※COG: 此类介质材料的电容器为 I 类电容器，包括常规、中高压 COG 产品。此类产品电性能稳定，几乎不随温度、电压和时间的变化而变化。适用于低损耗，稳定性要求高的电路中，如滤波器、谐振器和计时电路中。


※COG: The capacitor of this kind dielectric material is considered as Class I capacitor, including general capacitor and high frequency COG capacitor. The electrical properties of COG capacitor are the most stable one and have little change with temperature, voltage and time. They are suited for applications where low-losses and high-stability are required, such as filters, oscillators, and timing circuits.

※X7R、X5R、X6S、X7T: 此类介质材料的电容器为 II 类电容器，具有较高的介电常数，容量比 I 类电容器高，具有较稳定的温度特性，适用于容量范围广，稳定性要求不高的电路中，如隔直、耦合、旁路、鉴频等电路中。

※ X7R、X5R、X6S、X7T: material is a kind of material has high dielectric constant. The capacitor made of this kind material is considered as Class II capacitor whose capacitance is higher than that of class I . These capacitors are classified as having a semi-stable temperature characteristic and used over a wide temperature range, such in these kinds of circuits, DC-blocking, decoupling, bypassing, frequency discriminating etc.

※Y5V: 此类介质材料的电容器为 II 类电容器，是所有电容器中介电常数最大的电容器，但其容量稳定性较差，对温度、电压等条件较敏感，适用于要求大容量，温度变化不大的电路中。

※Y5V: The capacitor made of this kind of material is the highest dielectric constant of all ceramic capacitors. They are used over a moderate temperature range in application where high capacitance is required because of its unstable temperature coefficient, but where moderate losses and capacitance changes can be tolerated. Its capacitance and dissipation factors are sensible to measuring conditions, such as temperature and voltage, etc

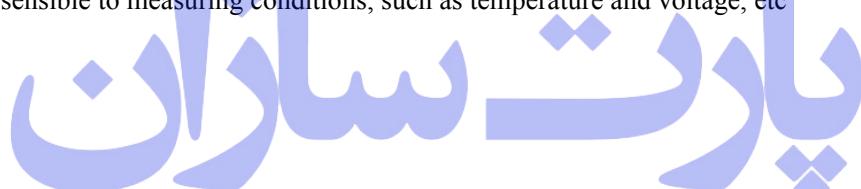

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923


E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214

Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

2. 产品结构 Product Frame

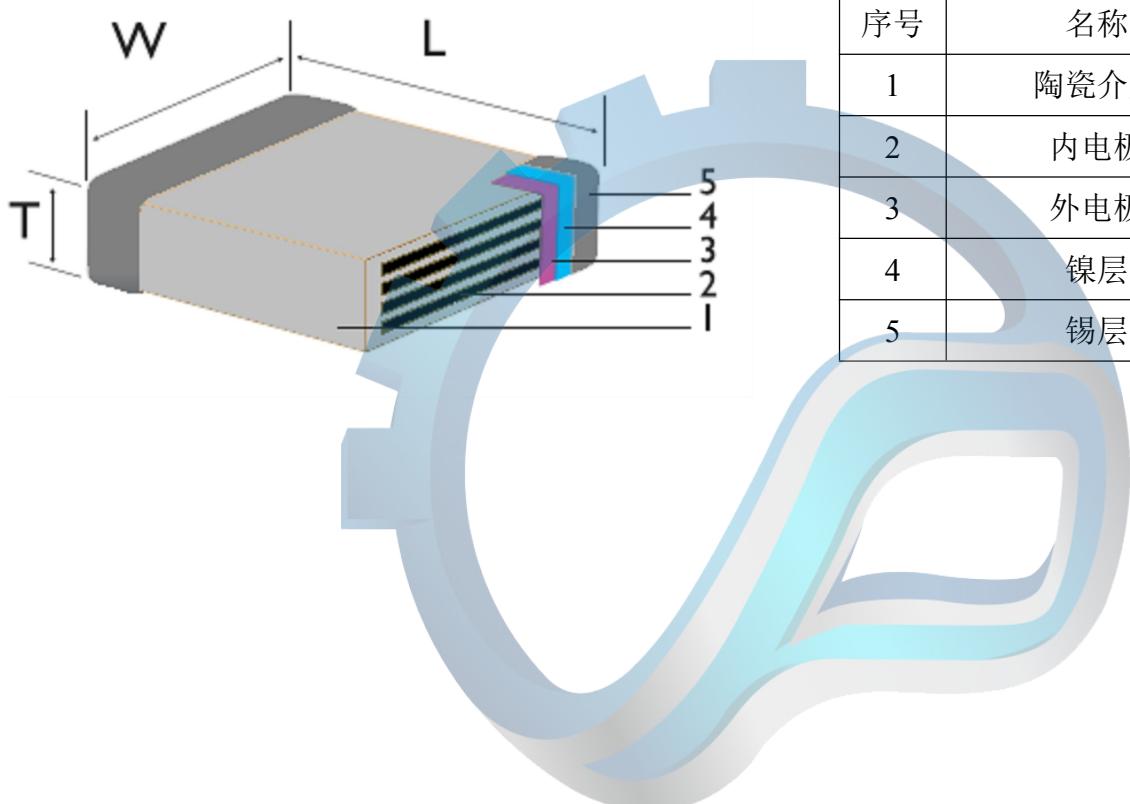

序号	名称
1	陶瓷介质
2	内电极
3	外电极
4	镍层
5	锡层

پارتسازان

PARTSAZAN Co.
@PARTSAZAN_LED
02166732484

电话(Tel) : 86-768-6855949, 685923

 E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928, 68559214

 Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

3. 产品规格型号命名规则

General Product Parts Numbering System

(例) (example)



产品的介质特性组别

材质	工作温度范围	温度系数或温度特性
C0G	-55°C~+125°C	0±30ppm/°C
X7R	-55°C~+125°C	±15%
X5R	-55°C~+85°C	±15%
X7T	-55°C~+125°C	+22/-33%
Y5V	-30°C~+85°C	+22/-82%
X6S	-55°C~+105°C	±22%

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel) : 86-768-6855949 , 685923

E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928 , 68559214

Website: <http://www.cctc.cc/>



潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646
ADD : San Huan Industrial District, Feng Tang Chao Zhou, GuangDong, China

产品标准书				编 号 Document No.							
SPECIFICATION FOR APPROVAL				DRAAW108J/0-2021							

4. 产品容量范围 Product Capacitance Range

0201(0603)尺寸

Cp V _{DC}	0201(0603)											
	X5R系列				X6S系列				X7T系列			
25	16	10	6.3	25	16	10	6.3	16	10	6.3	4	
103	Z				Z			Z				
223	Z	Z			Z	Z		Z	Z			
473	Z				Z			Z				
863		Z	Z		Z	Z		Z	Z			
104	Z	Z			Z	Z		Z	Z			
224			Z			Z					Z	

容量容差: X5R/X6S/X7T:; K($\pm 10\%$); M($\pm 20\%$)

厚度: Z: $0.30 \pm 0.03\text{mm}$;

以上容量仅供参考，具体容量取决于使用要求。

Tolerance: X5R/X6S/X7T: K($\pm 10\%$); M($\pm 20\%$)

Thickness: Z: $0.30 \pm 0.03\text{mm}$;

Above capacitance for reference only, actual cap. Range depends on the standard products.

پارتسازان

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214

Website: <http://www.cctc.cc/>

产品标准书 SPECIFICATIONFOR APPROVAL	编 号 Document No.
	DRAAW108J/0-2021

0402 (1005) 尺寸

Cp V _{DC}	0402(1005)																									
	COG系列		X7R系列				X6S系列				X5R系列				X7T系列				Y5V系列							
50	25	50	25	16	10	6.3	50	25	16	10	6.3	50	25	16	10	6.3	25	16	10	6.3	4	50	25	16	10	6.3
0R5	A	A																								
1R0	A	A																								
2R0	A	A																								
3R0	A	A																								
4R0	A	A																								
5R0	A	A																								
6R0	A	A																								
7R0	A	A																								
8R0	A	A																								
9R0	A	A																								
100	A	A																								
120	A	A																								
150	A	A																								
180	A	A																								
200	A	A																								
220	A	A																								
270	A	A																								
300	A	A																								
330	A	A																								
390	A	A																								
470	A	A																								
560	A	A																								
680	A	A																								
820	A	A																								
101	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
121	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
151	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
181	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
201	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
221	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
271	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
331	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
391	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
471	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
561	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
681	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
821	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		
102	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A		

**PARTSAZAN Co.
@PARTSAZAN_LED**

电话(Tel) : 86-768-6855949 , 685923

E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928 , 68559214

Website: <http://www.cctc.cc/>

产品标准书							编 号 Document No.														
SPECIFICATIONFOR APPROVAL							DRAAW108J/0-2021														

Cp V _{DC}	0402(1005)																									
	COG系列		X7R系列					X6S系列					X5R系列					X7T系列					Y5V系列			
50	25	50	25	16	10	6.3	50	25	16	10	6.3	50	25	16	10	6.3	25	16	10	6.3	4	50	25	16	10	6.3
152		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
182		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
222		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
272		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
332		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
472		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
562		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
103		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
153		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
183		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
223		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
273		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
333		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
393		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
473		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
563		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
683		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
104		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
154		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
184		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
224		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
274		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
334		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
474		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
684		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A
105		A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A	A

容量容差: COG(0.5pF~4.9pF): B/C; COG(5.0pF~9.9pF): D; COG(≥ 10 pF): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$), K($\pm 10\%$)

X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$)

Y5V: M($\pm 20\%$); Z(-20,+80%)

厚度: A: 0.50 ± 0.10 mm ;

以上容量仅供参考，具体容量取决于使用要求。

Tolerance: COG(0.5pF~4.9pF): C; COG(5.0pF~9.9pF): D; COG(≥ 10 pF): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$)

X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$)

Y5V: M($\pm 20\%$); Z(-20,+80%)

Thickness: A: 0.50 ± 0.10 mm ;

Above capacitance for reference only, actual cap. Range depends on the standard products.

产品标准书 SPECIFICATIONFOR APPROVAL	编 号 Document No.
	DRAAW108J/0-2021

0603(1608)尺寸

		0603(1608)																					
	COG系列	X7R系列						X6S系列						X5R系列						X7T系列			
Cp	V _{DC}	250	200	100	50	25	250	200	100	50	25	16	10	6.3	50	25	16	10	6.3	50	25	16	10
0R5	C	C	C	C	C	C																	
1R0	C	C	C	C	C	C																	
2R0	C	C	C	C	C	C																	
3R0	C	C	C	C	C	C																	
4R0	C	C	C	C	C	C																	
5R0	C	C	C	C	C	C																	
6R0	C	C	C	C	C	C																	
7R0	C	C	C	C	C	C																	
8R0	C	C	C	C	C	C																	
9R0	C	C	C	C	C	C																	
100	C	C	C	C	C	C																	
120	C	C	C	C	C	C																	
150	C	C	C	C	C	C																	
180	C	C	C	C	C	C																	
200	C	C	C	C	C	C																	
220	C	C	C	C	C	C																	
270	C	C	C	C	C	C																	
300	C	C	C	C	C	C																	
330	C	C	C	C	C	C																	
390	C	C	C	C	C	C																	
470	C	C	C	C	C	C																	
560	C	C	C	C	C	C																	
680	C	C	C	C	C	C																	
820	C	C	C	C	C	C																	
101	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
121	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
151	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
181	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
201	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
221	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
271	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
331	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
391	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
471	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
561		C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
681		C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
821		C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	
102			C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	

**PARTSAZAN Co.
@PARTSAZAN_LED**

电话(Tel) : 86-768-6855949 , 685923

 E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928 , 68559214

 Website: <http://www.cctc.cc/>

产品标准书 SPECIFICATIONFOR APPROVAL										编 号 Document No.																	
										DRAAW108J/0-2021																	

Cp	V _{DC}	0603(1608)																		Y5V系列													
		COG系列					X7R系列					X6S系列				XSR系列				X7T系列				25	16	10	6.3	4	50	25	16	10	
Cp	V _{DC}	250	200	100	50	25	250	200	100	50	25	16	10	6.3	50	25	16	10	6.3	50	25	16	10	6.3	25	16	10	6.3	4	50	25	16	10
152				C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
182				C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
222				C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
272				C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
332				C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
472				C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
562				C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
682				C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
103					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
153					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
183					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
223					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
273					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
333					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
393					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
473					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
563					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
683					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
104					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
154					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
184					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
224					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
274					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
334					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
474					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
684					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
105					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
225					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
475					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C
106					C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C	C

容量容差: COG(0.5pF~4.9pF): B/C; COG(5.0pF~9.9pF): D; COG(≥ 10 pF): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$), K($\pm 10\%$)

X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$); Y5V: M($\pm 20\%$); Z(-20,+80%)

厚度: C: 0.80 ± 0.1 mm (0.80 ± 0.2 mm) ; 以上容量仅供参考, 具体容量取决于使用要求。

Tolerance: COG(0.5pF~4.9pF): C COG(5.0pF~9.9pF): D; COG(≥ 10 pF): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$)

X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$); Y5V: M($\pm 20\%$); Z(-20,+80%)

Thickness: C: 0.80 ± 0.1 mm (0.80 ± 0.2 mm) ; Above capacitance for reference only, actual cap. Range depends on the standard products.

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 6855921

Website: <http://www.cctc.cc>



CCTC
三环集团

潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646

ADD : San Huan Industrial District , Feng Tang Chao Zhou, GuangDong, China

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

0805(2012)尺寸

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923
E-mail: market@china-threecircle.com

02166732484 (Fax): (768) 6855928, 68559214

Website: <http://www.cetc.com>



潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646
ADD : San Huan Industrial District, Feng Tang Chao Zhou, GuangDong, China

产品标准书 SPECIFICATION FOR APPROVAL										编 号 Document No. DRAAW108J/0-2021																			
										0805(2012)																			

Cp	V _{rc}	250	100	50	25	16	250	100	50	25	16	10	6.3	50	25	16	10	6.3	50	25	16	10	6.3	25	16	10	6.3	4	50	25	16	10	6.3	
152	B	B	B	B	B	D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
182		B	B	B	B	D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
222	B	B	B	B	D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
272		B	B	B	B	D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
332			D	D	D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
472			D	D	D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
562			D	D	D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
682			D	D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
103				D/F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
153			F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
183			F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
223			F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
273			F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
333			F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
393			F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
473			F	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
563				D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
683				D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
104				D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
154					D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
184					D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
224					D/F	D	D	D	D	D/F	D	D	D	D	D	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
274					D/F	D	D	D	D	D/F	D	D	D	D	D	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
334					D/F	D	D	D	D	D/F	D	D	D	D	D	D/F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
474					D/F	D/F	D/F	D	D	D/F	D/F	D/F	D	D	D	D/F	D/F	D/F	D	D	D/F	D/F	D/F	D	D	D	D/F	D/F	D/F	D	D			
684					D	D/F	D/F	D	D	D	D/F	D/F	D	D	D	D/F	D/F	D/F	D	D	D	D/F	D/F	D/F	D	D	D	D/F	D/F	D/F	D	D		
105					F	D/F	D/F	D	D	F	D/F	D/F	D	D	F	D/F	D/F	D	D	F	D/F	D/F	D	D	D	D	D	D/F	D/F	D/F	D	D		
225						F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F		
475						F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F		
106						F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F		
226						F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F		
476						F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F		

容量容差: COG(0.5pF~4.9pF): B/C; COG(5.0pF~9.9pF): D; COG(≥ 10 pF): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$), K($\pm 10\%$)

X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$); Y5V: M($\pm 20\%$); Z(-20,+80%)

厚度: B: 0.60 ± 0.1 mm、D: 0.85 ± 0.1 mm、F: 1.25 ± 0.2 mm; 以上容量仅供参考, 具体容量取决于使用要求。

Tolerance: COG(0.5pF~4.9pF): C COG(5.0pF~9.9pF): D; COG(≥ 10 pF): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$)

X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$); Y5V: M($\pm 20\%$); Z(-20,+80%)

Thickness: B: 0.60 ± 0.1 mm、D: 0.85 ± 0.1 mm、F: 1.25 ± 0.2 mm; Above capacitance for reference only, actual cap.

Range depends on the standard products.

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 6855921

网站: <http://www.cctc.cc>



潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646
ADD : San Huan Industrial District, Feng Tang Chao Zhou, GuangDong, China

产品标准书 SPECIFICATION FOR APPROVAL	编 号 Document No.
	DRAAW108J/0-2021

1206(3216)尺寸

Cp V _{DC}	1206(3216)																							
	COG系列					X7R系列					X6S系列					X5R系列					X7T系列			
0R5	D	D	D	D	D	D	D	D	D	D														
1R0	D	D	D	D	D	D	D	D	D	D														
2R0	D	D	D	D	D	D	D	D	D	D														
3R0	D	D	D	D	D	D	D	D	D	D														
4R0	D	D	D	D	D	D	D	D	D	D														
5R0	D	D	D	D	D	D	D	D	D	D														
6R0	D	D	D	D	D	D	D	D	D	D														
7R0	D	D	D	D	D	D	D	D	D	D														
8R0	D	D	D	D	D	D	D	D	D	D														
9R0	D	D	D	D	D	D	D	D	D	D														
100	D	D	D	D	D	D	D	D	D	D														
120	D	D	D	D	D	D	D	D	D	D														
150	D	D	D	D	D	D	D	D	D	D														
180	D	D	D	D	D	D	D	D	D	D														
200	D	D	D	D	D	D	D	D	D	D														
220	D/E/ F	D	D	D	D	D	D	D	D	D														
270	D/E/ F	D	D	D	D	D	D	D	D	D														
300	D/E/ F	D	D	D	D	D	D	D	D	D														
330	D/E/ F	D	D	D	D	D	D	D	D	D														
390	D/E/ F	D	D	D	D	D	D	D	D	D														
470	D/E/ F	D	D	D	D	D	D	D	D	D														
560	D/E/ F	D	D	D	D	D	D	D	D	D														
680	D/E/ F	D	D	D	D	D	D	D	D	D														
820	D/E/ F	D	D	D	D	D	D	D	D	D														
101	D/E/ F	D	D	D	D	D	D	D	F	F	F	F	F	F										
121	D/E/ F	D	D	D	D	D	D	D	F	F	F	F	F	F										
151	D/E	D	D	D	D	D	D	D	F	F	F	F	F	F										
181	D/E	D	D	D	D	D	D	D	F	F	F	F	F	F										
201	D/E	D	D	D	D	D	D	D	F	F	F	F	F	F										
221	D/E	D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	
271	D/E	D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	
331	D/E	D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	
391	D/E	D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	
471	D/E	D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	
561		D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	
681		D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	
821		D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	
102		D	D	D	D	D	D	D	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel) : 86-768-6855949 , 685923

E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928 , 68559214

Website: <http://www.cctc.cc/>



潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646
ADD : San Huan Industrial District, Feng Tang Chao Zhou, GuangDong, China

产品标准书														编 号 Document No.													
SPECIFICATIONFOR APPROVAL														DRAAW108J/0-2021													

1206(3216)																															
Cap V _{DC}	COG系列							X7R系列							X6S系列				X5R系列				X7T系列				Y5V系列				
	2000	1000	630	500	250	100	50	25	16	2000	1000	630	500	250	100	50	25	16	10	6.3	50	25	16	10	6.3	4	50	25	16	10	6.3
152		D	D	D	D	D	D	D	D	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
182			D	D	D	D	D	D	D	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
222			D	D	D	D	D	D	D	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
272			D	D	D	D	D	D	D	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
332			D	D	D	D	D	D	D	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
472			D	D	D	D	D	D	D	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
562			D	D	D	D	D	D	D	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
682				D	D	D	D	D	D	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
103				P	F	F	F	F	F	F	F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	
153										F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
183										F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
223										F	F	F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
273										F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
333										F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
393										F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
473										F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
533										F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
683										F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
104										F	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
154										D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
184										D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
224										D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
274										D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
334										D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D	D
474										F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F
684										F/H	F/H	F	F	F	F	F/H	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F
105										F/H	F/H	F	F	F	F	F/H*	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F
205										F/H*	E	E	E	E	E	E	E	E	E	E	E	E	E	E	E	E	E	E	E	E	E
225										F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F	F
475										H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	
106										H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*
226										H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*
476										H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*	H/H*

容量容差: COG(0.5pF~4.9pF): B/C; COG(5.0pF~9.9pF): D; COG(≥ 10 pF): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$), K($\pm 10\%$)

X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$); Y5V: M($\pm 20\%$); Z(-20,+80%)

厚度: D: 0.85 ± 0.1 mm、E: 1.00 ± 0.1 mm、F: 1.25 ± 0.2 mm、H: 1.60 ± 0.2 mm、 $1.60 \pm 0.3^*$ mm; 以上容量仅供参考，具体容量取决于使用要求。

Tolerance: COG(0.5pF~4.9pF): C ;COG(5.0pF~9.9pF): D; COG(≥ 10 pF): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$)

X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$); Y5V: M($\pm 20\%$); Z(-20,+80%)

Thickness: D: 0.85 ± 0.1 mm、E: 1.00 ± 0.1 mm、F: 1.25 ± 0.2 mm、H: 1.60 ± 0.2 mm、 $1.60 \pm 0.3^*$ mm; Above capacitance for reference only, actual cap. Range depends on the standard products.

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214

Website: http://www.cctc.cc/

产品标准书 SPECIFICATION FOR APPROVAL	编 号 Document No.
	DRAAW108J/0-2021

1210(3225)尺寸

Cp V _{DC}	1210(3225)																																				
	COG系列					XTR系列					XGS系列				XSR系列				XTT系列				YSV系列														
2000	1000	500	250	100	50	2000	1000	630	500	250	100	50	25	16	10	6.3	50	25	16	10	6.3	50	25	16	10	6.3	25	16	10	6.3	4	50	25	16	10	6.3	
100	D																																				
120	D																																				
150	D																																				
180	D																																				
200	D																																				
220	D																																				
270	D																																				
300	D																																				
330	D																																				
390	D																																				
470	D																																				
560	D																																				
680	D																																				
820	D																																				
101	D	D	D	D	D																																
121	F	D	D	D	D																																
151	F	D	D	D	D																																
181	F	D	D	D	D																																
201	F	D	D	D	D																																
221	F	D	D	D	D																																
271		D	D	D	D																																
331		D	D	D	D																																
391		D	D	D	D																																
471		D	D	D	D																																
561		F	D	D	D																																
681		F	D	D	D																																
821		F	D	D	D																																
102		F	D	D	D																																
152			D	D	D																																
182			D	D	D																																
222			D	D	D																																
272			F	D	D																																
332				D	D																																
472				D																																	
562																																					
682																																					
103																																					
153																																					
223																																					
333																																					
473																																					
563																																					
683																																					
104																																					
154																																					
224																																					
334																																					
394																																					
474																																					
684																																					
105																																					
225																																					
475																																					
106																																					
226																																					
476																																					
107																																					

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel) : 86-768-6855949 , 685923

 E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928 ,



潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code) : 515646
ADD : San Huan Industrial District, Feng Tang Chao Zhou, GuangDong, China

产品标准书 SPECIFICATION FOR APPROVAL	编 号 Document No. DRAAW108J/0-2021
--	---

容量容差: COG($\geq 10\text{pF}$): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$), K($\pm 10\%$); X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$); Y5V: M($\pm 20\%$); Z(-20,+80%)


厚度: D: $0.85 \pm 0.1\text{mm}$ 、F: $1.25 \pm 0.2\text{mm}$ 、H: $1.60 \pm 0.2\text{mm}$ 、G: $2.00 \pm 0.20\text{mm}$ 、M: $2.50 \pm 0.30\text{mm}$;

以上容量仅供参考，具体容量取决于使用要求。

Tolerance: COG($\geq 10\text{pF}$): F($\pm 1\%$), G($\pm 2\%$), J($\pm 5\%$); X7R/X5R/X6S/X7T: J($\pm 5.0\%$); K($\pm 10\%$); M($\pm 20\%$); Y5V: M($\pm 20\%$); Z(-20,+80%)

Thickness: D: $0.85 \pm 0.1\text{mm}$ 、F: $1.25 \pm 0.2\text{mm}$ 、H: $1.60 \pm 0.2\text{mm}$ 、G: $2.00 \pm 0.20\text{mm}$ 、M: $2.50 \pm 0.30\text{mm}$;

Above capacitance for reference only, actual cap. Range depends on the standard products.

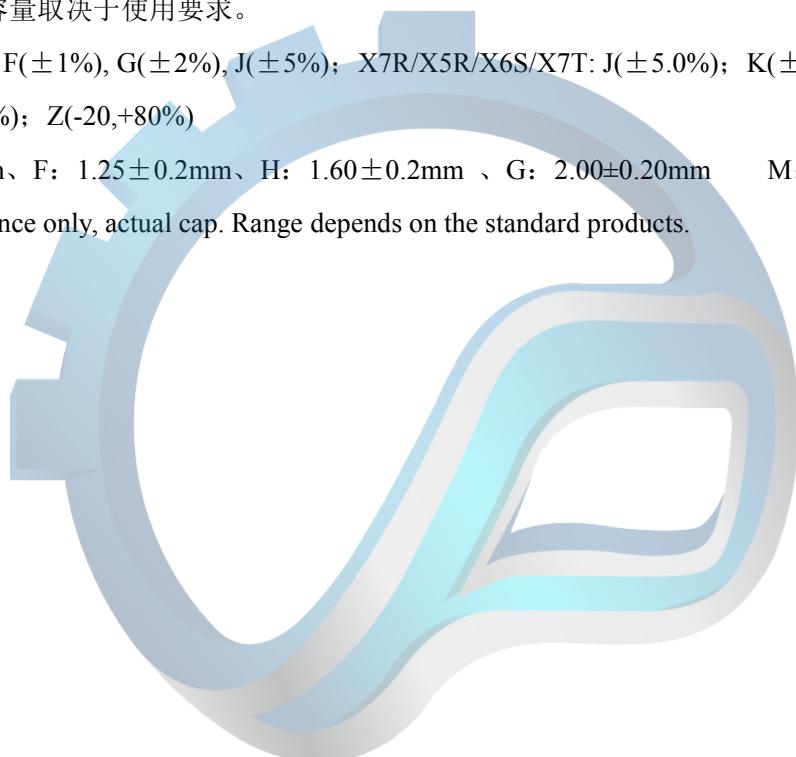

پارت سازان

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214


Website: <http://www.cctc.cc/>

产品标准书 SPECIFICATION FOR APPROVAL	编 号 Document No.
	DRAAW108J/0-2021

5. 产品尺寸 Dimensions


规格: 0201、0402、0603、0805、1206、1210。

Chip Size: 0201,0402,0603,0805,1206 and 1210

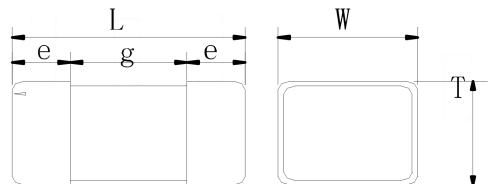

规格 Type	L (mm)	W (mm)	e (mm)	g min (mm)	T (mm)				
					0.30±0.03	0.50±0.10	0.80±0.10	1.25±0.20	1.25±0.20
0201	0.60±0.03	0.30±0.03	0.1~0.2	0.2	0.30±0.03	—	—	—	—
0402	1.00±0.10	0.50±0.10	0.15~0.3	0.4	0.50±0.10	—	—	—	—
0603	1.60±0.10	0.80±0.10	0.2~0.6	0.5	0.80±0.10	—	—	—	—
0603 ^{*1}	1.60±0.20 ^{*1}	0.80±0.20 ^{*1}	0.2~0.6	0.5	0.80±0.20 ^{*1}	—	—	—	—
0805	2.00±0.10	1.25±0.10	0.2~0.7	0.7	0.60±0.10	0.85±0.10	1.25±0.20	—	—
0805 ^{*1}	2.00±0.20 ^{*1}	1.25±0.20 ^{*1}	0.2~0.7	0.7	0.60±0.10	0.85±0.10	1.25±0.20	—	—
1206	3.20±0.20	1.60±0.20	0.3~0.8	1.6	0.85±0.10	1.00±0.10	1.25±0.20	1.60±0.20	—
1206 ^{*1}	3.20±0.30 ^{*1}	1.60±0.30 ^{*1}	0.3~0.8	1.6	0.85±0.10	1.00±0.10	1.25±0.20	1.60±0.30 ^{*1}	—
1210	3.20±0.30	2.5±0.20	0.3~0.8	1.6	0.85±0.10	1.25±0.20	1.60±0.20	2.00±0.20	2.50±0.30
1210 ^{*1}	3.20±0.40 ^{*1}	2.5±0.30 ^{*1}	0.3~0.8	1.6	0.85±0.10	1.25±0.20	1.60±0.20	2.00±0.20	2.50±0.30

*1 标识该规格型号标识为 1uF 及以上规格产品尺寸。

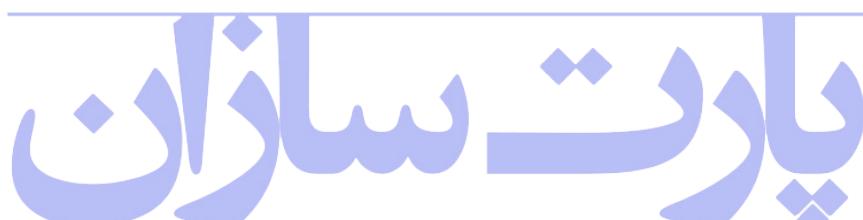

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214

Website: <http://www.cctc.cc/>



潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646
ADD : San Huan Industrial District, Feng Tang Chao Zhou, GuangDong, China

产品 标 准 书 SPECIFICATIONFOR APPROVAL	编 号 Document No. DRAAW108J/0-2021
--	---

6. 技术要求和测试条件 Specification and Test Condition

6.1 外观 Appearance

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG/X7R/X5R/Y5V/ X7T/X6S	1/10L < L ≤ 1/8L, 1/10W < w ≤ 1/8W, 1/10T < t ≤ 1/8T (l、w、t 任意一项不符 合, 均判定不合格) (l、w、t None is acceptable, All judged unqualified)	目视检查 Visual inspection.

6.2 尺寸 Dimensions

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG/X7R/X5R/Y5V/ X7T/X6S	在要求的范围内 Within the specified dimensions	用千分尺 Using calipers on micrometer

6.3 容量 Capacitance

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG	在要求的容值容差范围内 Within the specified tolerance A:±0.05pF;B:±0.1pF;C:±0.25pF; D:±0.5pF;J: ±5%	1.0±0.2VRms, 1MHz±10% (C>1000 pF, 1.0±0.2VRms, 1KHz±10%,)
X7R/X5R/X7T/ X6S	在要求的容值容差范围内 Within the specified tolerance J: ±5%; K: ±10%; M: ±20%	1.0±0.2VRms, 1KHz±10% (Cp>10uF, 0.5±0.1VRms, 120±24Hz)
Y5V	在要求的容值容差范围内 Within the specified tolerance M: ±20%; Z: -20%, +80%	1.0±0.2VRms, 1KHz±10% (Cp>10uF, 0.5±0.1VRms, 120±24Hz)

备注：测试温度：25°C ±3°C，测试湿度：<70%RH. 针对二类介质规格需去老化处理，条件：电容器在150°C热处理1小时，放置48h后进行测量。

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel)：86-768-6855949, 685923
E-mail: market@china-threecircle.com

传真(Fax)：(768) 6855928, 6855921
Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATIONFOR APPROVAL	DRAAW108J/0-2021

6.4 损耗 Dissipation Factor

类型 Dielectrics	技术要求 Specification			测试条件 Testing Condition																		
COG	Cp<30pF, Q≥400+20Cp; Cp≥30pF, Q≥1000			1.0±0.2Vrms, 1MHz±10%, 25°C (Cp>1000pF, 1.0±0.2Vrms, 1KHz±10%)																		
X7R/X5R/X7T/ X6S	0201	≤25V	C≤0.22 μF	≤10%																		
		≤25V	C≤0.47 μF	≤7.0%																		
		C>0.47 μF		≤10%																		
		>25V	C≤0.1 μF	≤7.0%																		
	0402	C>0.1 μF		≤10%																		
		≤25V	C≤0.47 μF	≤7.0%																		
		C>0.47 μF		≤10.0%																		
		>25V	C≤0.1 μF	≤5.0%																		
	0603	0.1 μF<C≤0.22 μF		≤7.0%																		
		C>0.22 μF		≤10%																		
		≤25V	C≤1 μF	≤7.0%																		
		C>1 μF		≤10.0%																		
	0805	>25V	C≤0.47 μF	≤7.0%																		
		C>0.47 μF		≤10.0%																		
		≤25V	C<2.2 μF	≤7.0%																		
		2.2 μF≤C<47 μF		≤10.0%																		
	1206	>25V	C<1 μF	≤7.0%																		
		1 μF≤C<47 μF		≤10.0%																		
		≤25V	C<2.2 μF	≤7.0%																		
		2.2 μF≤C<47 μF		≤10.0%																		
Y5V	<table border="1" style="width: 100%; border-collapse: collapse;"> <thead> <tr> <th>Ur</th> <th>DF</th> <th>备注</th> </tr> </thead> <tbody> <tr> <td>UR≥50V</td> <td>DF≤7.0%</td> <td></td> </tr> <tr> <td>UR=25V</td> <td>DF≤7.0%</td> <td>683>0402≥473, 474>0603≥104, 105>0805≥334, 475>1206≥684, 106>1210≥105</td> </tr> <tr> <td>UR=16V</td> <td>DF≤9.0%</td> <td>0402≥683, 0603≥474, 0805≥105, 1206≥475, 1210≥106</td> </tr> <tr> <td>UR=10V</td> <td>DF≤12.5%</td> <td>0402≥224, 0603≥225, 0805≥335, 1206≥106, 1210≥226, 1812≥476</td> </tr> <tr> <td>UR=6.3V</td> <td>DF≤15.0%</td> <td></td> </tr> </tbody> </table>			Ur	DF	备注	UR≥50V	DF≤7.0%		UR=25V	DF≤7.0%	683>0402≥473, 474>0603≥104, 105>0805≥334, 475>1206≥684, 106>1210≥105	UR=16V	DF≤9.0%	0402≥683, 0603≥474, 0805≥105, 1206≥475, 1210≥106	UR=10V	DF≤12.5%	0402≥224, 0603≥225, 0805≥335, 1206≥106, 1210≥226, 1812≥476	UR=6.3V	DF≤15.0%		1.0±0.2Vrms, 1KHz±10%, (Cp>10uF, 0.5±0.1Vrms, 120±24Hz)
Ur	DF	备注																				
UR≥50V	DF≤7.0%																					
UR=25V	DF≤7.0%	683>0402≥473, 474>0603≥104, 105>0805≥334, 475>1206≥684, 106>1210≥105																				
UR=16V	DF≤9.0%	0402≥683, 0603≥474, 0805≥105, 1206≥475, 1210≥106																				
UR=10V	DF≤12.5%	0402≥224, 0603≥225, 0805≥335, 1206≥106, 1210≥226, 1812≥476																				
UR=6.3V	DF≤15.0%																					
25°C, 预处理后 48hrs。 at 25°C, 48hrs after annealing																						
备注： 测试温度： 25°C ±3°C， 测试湿度： <70%RH. 针对二类介质规格需去老化处理， 条件： 电容器在 150°C热处理 1 小时， 放置 48h 后进行测量。																						

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel) : 86-768-6855949, 685923

传真(Fax) : (768) 6855928, 6855921

 E-mail: market@china-threecircle.com

 Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATIONFOR APPROVAL	DRAAW108J/0-2021

6.5 绝缘电阻 Insulation Resistance

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG/X7R/ X5R/Y5V/X7T/ X6S	UR≤50V, 大于 10 GΩ 或 100Ω·F /CR(大于其中较小的数值) UR≤50V , More than 10 GΩ or 100Ω·F /CR, whichever is smaller.	UR≤50V U _测 =UR ; 充电时间:60±5 秒 温度:25°C Charge Time:60±5sec Temperture:25°C
COG/X7R/X7T/ X6S	UR>50V, 大于 4GΩ 或 100Ω·F/CR (大于其中较小的数值) UR > 50V , More than 4 GΩ or 100Ω·F/CR , whichever is smaller.	UR≤400V U _测 =UR UR>400V U _测 =400V; 充电时间:60±5 秒 温度:25°C Charge Time:60±5sec Temperture:25°C

备注：测试温度：25°C±3°C， 测试湿度：<70%RH.

6.6 耐电压 Dielectric Strength

类型 Dielectrics	额定电压范围 Rated voltage range	耐电压性能测试方法 Measuring Method
COG	UR≤50V	施加额定电压的 300%,5 秒,最大电流不超过 50mA Force 300%Rated voltage for 5second. Max..current should not exceed 50 mA.
X7R/X5R/Y5V/X7T/ X6S	UR≤50V	施加额定电压的 250%,5 秒,最大电流不超过 50mA Force 250%Rated voltage for 5second. Max..current should not exceed 50 mA.
COG/X7R/X7T	100V≤UR<500V	施加额定电压的 200%,5 秒,最大电流不超过 50mA Force 200%Rated voltage for 5second. Max..current should not exceed 50 mA.
	500V≤UR<1000V	施加额定电压的 150%,5 秒,最大电流不超过 50mA Force 150% Rated voltage for 5second. Max..current should not exceed 50 mA.
	1000V≤UR<2000V	施加额定电压的 150%,5 秒,最大电流不超过 50mA Force 150%Rated voltage for 5second. Max..current should not exceed 50 mA.
	UR≥2000V	施加额定电压的 120%,5 秒,最大电流不超过 30mA Force 120%Rated voltage for 5second. Max..current should not exceed 30 mA.

PARTSAZAN Co.

@PARTSAZAN_LED

02166732484

电话(Tel)：86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax)：(768) 6855928, 68559214

Website: <http://www.cctc.cc/>



CCTC
三环集团

潮州三环（集团）股份有限公司
Chaozhou Three-Circle (Group) Co., Ltd.

地址：廣東省潮州市鳳塘三環工業城 郵編(Post Code)：515646
ADD : San Huan Industrial District, Feng Tang Chao Zhou, GuangDong, China

产品标准书 SPECIFICATION FOR APPROVAL	编 号 Document No. DRAAW108J/0-2021
---	--

6.7 静电容量温度特性 Temperature Coefficient of Capacitance

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition				
		步骤 STEP	COG, X7R,X7T	X6S	X5R	Y5V
COG	容量变化在±30ppm/°C 以内 容量漂移在±0.2% 或±0.05pF 以内 Temperature coefficient within ±30ppm/°C; Cp drift within ±0.2% or ±0.05pF	1	25 ±2	25 ±2	25 ±2	25 ±2
		2	-55±3	-55±3	-55±3	-30±3
X7R/X5R	容量变化在±15%以内 Capacitance change within ±15%	3	25 ±2	25 ±2	25 ±2	25 ±2
		4	125±3	105±3	85±3	85±3
		5	25 ±2	25 ±2	25 ±2	25 ±2
X7T	容量变化在+22%, -33%以内 Capacitance change within +22%, -33%	1) COG 容量漂移的计算方法为：用步骤 3 测量的电容容值量除以在第 1、3 和 5 步骤测量得到的误差的最大值和最小值的差。 温度系数的计算以第 3 步骤测量电容容量为参考。 The capacitance drift is calculated by dividing the differences between the maximum and minimum measured values in the step 1,3 and 5. The temperature coefficient is determined using the Capacitance measured in step 3 as a reference.				
X6S	容量变化在±22%以内 Capacitance change within ±22%	2) X7R、X5R、X7T、X6S 和 Y5V 与 25°C 时的电容容量相比较，电容容量在温度范围内的变化在要求的范围之内。 X7R、X5R、X7T、X6S and Y5V The ranges of capacitance change compared within the above 25 °C value over the temperature ranges shall be within the specified ranges.				
Y5V	容量变化在+22%, -82%以内 Capacitance change within +22%, -82%					

PARTSAZAN Co.

@PARTSAZAN_LED

02166732484

电话(Tel) : 86-768-6855949, 685923


E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928, 68559214

Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

6.8 附着力 Adhesion

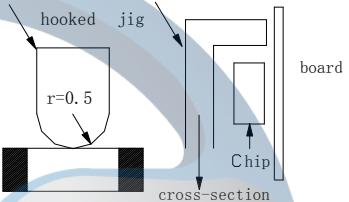类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG/X7R/X5R/ Y5V/X7T/X6S	端电极无松动，也无其它不良现象 No removal of the terminations or other defect shall occur.	施加 6N 的压力，并保持 10±1 秒 The pressurizing force shall be 6N (=600g*f) and the duration of application shall be 10±1sec.  cross-section

6.9 可焊性 Solderability of Termination

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG X7R/X5R Y5V/X7T/X6S	端电极挂锡面积不小于 95%，针孔或粗糙面积小于 5% 95% min. coverage of both terminal electrodes and less than 5% have pin holes or rough spots.	锡炉温度: 245±5°C 浸入时间: 2±1 秒 两侧端电极完全浸入焊锡炉 Solder temperature: 245±5°C Dipping time: 2±1 seconds. Completely soak both terminal electrodes in solder

6.10 耐焊性 Resistance to leaching

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG X7R/X5R Y5V/X7T/X6S	端电极挂锡面积不小于 95%，针孔或粗糙面积小于 5%，外观无开裂 95% min. coverage of both terminal electrodes and less than 5% have pin holes or rough spots. No remarkable visual damage.	预热: 120°C~150°C/60 秒 锡炉温度: 270±5°C 浸入时间: 10±1 秒 两侧端电极完全浸入焊锡炉 Solder temperature: 270±5°C preheated: 120°C~150°C/60sec Dipping time: 10±1 seconds. Completely soak both terminal electrodes in solder

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923



E-mail: market@china-threecircle.com


传真(Fax): (768) 6855928, 68559214

Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

6.11 端电极结合强度 Bending

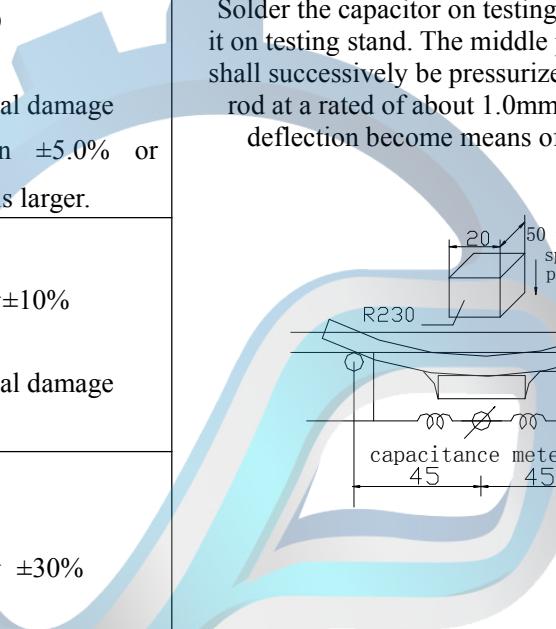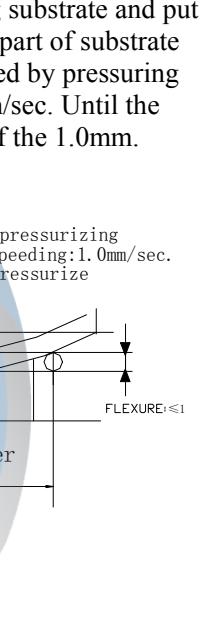类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG	无可见损伤； 容量变化小于等于±5%或±0.5pF (取较大值) No remarkable visual damage Cp change within ±5.0% or ±0.5pF, whichever is larger.	将片状电容器安装在测试夹具上，按图所示方向以1.0mm/s的速率施加压力，弯曲1mm。 Solder the capacitor on testing substrate and put it on testing stand. The middle part of substrate shall successively be pressurized by pressuring rod at a rated of about 1.0mm/sec. Until the deflection become means of the 1.0mm.
X7R/X5R/X7T/ X6S	无可见损伤； 容量变化小于等于±10% No remarkable visual damage Cp change ≤±10%	
Y5V	无可见损伤； 容量变化小于等于±30% No remarkable visual damage Cp change ≤±30%	

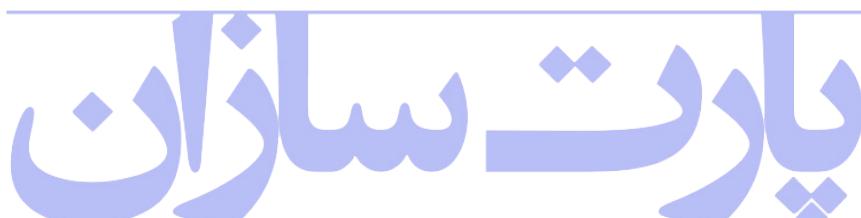

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel) : 86-768-6855949, 685923
 E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928, 68559214

Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

6.12 耐焊接热 Resistance to Soldering Heat

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG	<p>无明显可见损伤 容量变化在$\pm 2.5\%$或$\pm 0.25\text{pF}$(取较大值) 以内 DF 满足产品初始值的要求 IR 满足产品初始值的要求</p> <p>No remarkable visual damage Cp change within $\pm 2.5\%$ or $\pm 0.25\text{pF}$, whichever is larger. DF meets initial standard value. IR meets initial standard value.</p>	<p>焊接温度: $270 \pm 5^\circ\text{C}$ 预热: $120 \sim 150^\circ\text{C}$ 60 秒 浸入时间: 10 ± 1 秒 在室温下放置 24 ± 2 (COG) 或 48 ± 4 (X7R、X5R、Y5V、X7T、X6S) 小时以后测量 试验后在标准条件下恢复</p> <p>*高介电常数电容器的初始值测量 在 $140 \sim 150^\circ\text{C}$ 进行 1 小时的热处理后在室温下放置 48 ± 4 小时 测量初始值</p> <p>Soldering temperature: $270 \pm 5^\circ\text{C}$ Preheating: $120 \sim 150^\circ\text{C}$ 60sec. Dipping time: 10 ± 1 seconds. Measurement to be made after being kept at room temperature for 24 ± 2 (COG) or 48 ± 4 (X7R, X5R, Y5V, X7T, X6S) hours. Recovery for the following period under the standard condition after test.</p> <p>*Initial measurement for high dielectric constant type Perform a heat treatment at $140 \sim 150^\circ\text{C}$ for 1hr and let sit for 48 ± 4hrs at room temperature. Perform the initial measurement.</p>
X7R/X5R/X7T/X6S	<p>无明显可见损伤 容量变化在$\pm 7.5\%$以内 DF 满足产品初始值的要求 IR 满足产品初始值的要求</p> <p>No remarkable visual damage Cp change within $\pm 7.5\%$ DF meets initial standard value. IR meets initial standard value.</p>	<p>Soldering temperature: $270 \pm 5^\circ\text{C}$ Preheating: $120 \sim 150^\circ\text{C}$ 60sec. Dipping time: 10 ± 1 seconds. Measurement to be made after being kept at room temperature for 24 ± 2 (COG) or 48 ± 4 (X7R, X5R, Y5V, X7T, X6S) hours. Recovery for the following period under the standard condition after test.</p> <p>*Initial measurement for high dielectric constant type Perform a heat treatment at $140 \sim 150^\circ\text{C}$ for 1hr and let sit for 48 ± 4hrs at room temperature. Perform the initial measurement.</p>
Y5V	<p>无明显可见损伤 容量变化在$\pm 20\%$以内 DF 满足产品初始值的要求 IR 满足产品初始值的要求</p> <p>No remarkable visual damage Cp change within $\pm 20\%$ DF meets initial standard value. IR meets initial standard value.</p>	<p>Soldering temperature: $270 \pm 5^\circ\text{C}$ Preheating: $120 \sim 150^\circ\text{C}$ 60sec. Dipping time: 10 ± 1 seconds. Measurement to be made after being kept at room temperature for 24 ± 2 (COG) or 48 ± 4 (X7R, X5R, Y5V, X7T, X6S) hours. Recovery for the following period under the standard condition after test.</p> <p>*Initial measurement for high dielectric constant type Perform a heat treatment at $140 \sim 150^\circ\text{C}$ for 1hr and let sit for 48 ± 4hrs at room temperature. Perform the initial measurement.</p>

PARTSAZAN Co.
@PARTSAZAN_LED
02166732484

电话(Tel): 86-768-6855949, 685923

 E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214

 Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

6.13 温度快速循环 Temperature Cycle

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition															
COG	<p>无明显可见损伤 容量变化在$\pm 2.5\%$或 $\pm 0.25\text{pF}$ (取较大值) 以内</p> <p>No remarkable visual damage Cp change within $\pm 2.5\%$ or $\pm 0.25\text{pF}$, whichever is larger.</p>	<p>按下列步骤进行 5 次循环: To perform 5 cycles of the stated environment</p> <table border="1" style="margin-left: 20px;"> <thead> <tr> <th style="text-align: left;">步 骤 Step</th> <th style="text-align: left;">温 度 Temperature</th> <th style="text-align: left;">时 间 Time</th> </tr> </thead> <tbody> <tr> <td>1</td> <td>下限类别温度 $+0/-3^\circ\text{C}$</td> <td>30min</td> </tr> <tr> <td>2</td> <td>25°C</td> <td>2~3 min</td> </tr> <tr> <td>3</td> <td>上限类别温度 $+3/-0^\circ\text{C}$</td> <td>30 min</td> </tr> <tr> <td>4</td> <td>25°C</td> <td>2~3 min</td> </tr> </tbody> </table> <p>在室温下放置 48 ± 4 X7R, X5R, Y5V、X7T、X6S) 小时以后测量 *高介电常数电容器的初始值测量 在 $140\sim 150^\circ\text{C}$ 进行 1 小时的热处理后 在室温下放置 48 ± 4 小时 测量初始值 Measurement to be made after being kept at room temperature for 24 ± 2 hrs (COG) or 48 ± 4 hrs (X7R, X5R, Y5V, X7T, X6S) at room temperature, then measure. *Initial measurement for high dielectric constant type Perform a heat treatment at $140\sim 150^\circ\text{C}$ for 1hr and let sit for 48 ± 4 hrs at room temperature. Perform the initial measurement.</p>	步 骤 Step	温 度 Temperature	时 间 Time	1	下限类别温度 $+0/-3^\circ\text{C}$	30min	2	25°C	2~3 min	3	上限类别温度 $+3/-0^\circ\text{C}$	30 min	4	25°C	2~3 min
步 骤 Step	温 度 Temperature	时 间 Time															
1	下限类别温度 $+0/-3^\circ\text{C}$	30min															
2	25°C	2~3 min															
3	上限类别温度 $+3/-0^\circ\text{C}$	30 min															
4	25°C	2~3 min															
X7R/X5R/X7T/X6S	<p>无明显可见损伤 容量变化在$\pm 7.5\%$以内</p> <p>No remarkable visual damage Cp change within $\pm 7.5\%$</p>																
Y5V	<p>无明显可见损伤 容量变化在$\pm 20\%$以内</p> <p>No remarkable visual damage Cp change within $\pm 20\%$</p>																

PARTSAZAN Co.
@PARTSAZAN_LED
02166732484
电话(Tel) : 86-768-6855949, 685923
E-mail: market@china-threecircle.com
传真(Fax) : (768) 6855928, 68559214
Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATIONFOR APPROVAL	DRAAW108J/0-2021

6.14 稳态湿热 Moisture Resistance ,steady state

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG	<p>外观无明显可见损伤 容量变化在±5%或 ±0.5pF (取较大值) 以内 $C_p < 10\text{pF}$, $Q \geq 200+10C_p$; $10 \leq C_p < 30\text{pF}$, $Q \geq 275+2.5C_p$ $C_p \geq 30\text{pF}$, $Q \geq 350$ IR: 大于 $1000\text{M}\Omega$ 或 $10\Omega \cdot \text{F}$(取较小值)</p> <p>No remarkable visual damage C_p change within ±5% or ±0.5pF, whichever is larger. $C_p < 10\text{pF}$, $Q \geq 200+10C_p$; $10 \leq C_p < 30\text{pF}$, $Q \geq 275+2.5C_p$ $C_p \geq 30\text{pF}$, $Q \geq 350$ $R \cdot C \geq 1000\text{M}\Omega$ or $10\Omega \cdot \text{F}$, whichever is smaller</p>	<p>测试温度: $40 \pm 2^\circ\text{C}$ 湿度: 90~95% RH 测试时间: $500 \pm 12\text{hrs}$</p> <p>在室温下放置 24 ± 2 (COG) 或 48 ± 4(X7R、X5R、Y5V、X7T、X6S) 小时以后测量</p> <p>*高介电常数电容器的初始值测量 在 $140 \sim 150^\circ\text{C}$ 进行 1 小时的热处理 后在室温下放置 48 ± 4 小时 测量初始值</p> <p>Test temperature: $40 \pm 2^\circ\text{C}$ Humidity: 90~95% RH Testing time: $500 \pm 12\text{hrs}$</p> <p>Measurement to be made after being kept at room temperature for $24 \pm 2\text{hrs}$ (COG) or $48 \pm 4\text{hrs}$ (X7R, X5R, Y5V, X7T, X6S)</p> <p>*Initial measurement for high dielectric constant type Perform a heat treatment at $140 \sim 150^\circ\text{C}$ for 1hr and let sit for $48 \pm 4\text{hrs}$ at room temperature. Perform the initial measurement.</p>
X7R/X5R/X7T/ X6S	<p>外观无明显可见损伤 容量变化在±12.5%以内 DF 为初始值的 2 倍以下 IR: 大于 $1000\text{M}\Omega$ 或 $10\Omega \cdot \text{F}$(取较小值)</p> <p>C_p change within ±12.5% DF: Not more than 2 times of initial value $R \cdot C \geq 1000\text{M}\Omega$ or $10\Omega \cdot \text{F}$, whichever is smaller</p>	
Y5V	<p>外观无明显可见损伤 容量变化在±30%以内 DF 为初始值的 1.5 倍以下 IR: 大于 $1000\text{M}\Omega$ 或 $10\Omega \cdot \text{F}$(取较小值)</p> <p>No remarkable visual damage C_p change within ±30% DF: Not more than 1.5 times of initial value $R \cdot C \geq 1000\text{M}\Omega$ or $10\Omega \cdot \text{F}$, whichever is smaller</p>	

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923

 E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 6855921

 Website: <http://www.cctc.cc/>



产品标准书 SPECIFICATION FOR APPROVAL	编 号 Document No. DRAAW108J/0-2021
--	---

6.15 耐湿负荷 Damp heat with load

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG	外观无明显可见损伤 容量变化在±7.5%或±0.75pF (取较大值) 以内 $C_p < 30\text{pF}$, $Q \geq 100 + 10/3 * C_p$ $C_p \geq 30\text{pF}$, $Q \geq 200$ IR: 大于 $500\text{M}\Omega$ 或 $5\Omega \cdot \text{F}$ (取较小值) No remarkable visual damage $C_p \text{ change} \leq \pm 7.5\%$ or $\pm 0.75\text{pF}$, whichever is larger. $C_p < 30\text{pF}$, $Q \geq 100 + 10/3 * C_p$ $C_p \geq 30\text{pF}$, $Q \geq 200$ $R * C \geq 500\text{M}\Omega$ or $5\Omega \cdot \text{F}$, whichever is smaller	测试温度: $40 \pm 2^\circ\text{C}$ 湿度: 90~95% RH 电压: 额定电压 测试时间: $500 \pm 12\text{hrs}$ 在室温下放置 24 ± 2 (COG) 或 48 ± 4 (X7R、X5R、Y5V、X7T、X6S) 小时以后测量 *在 $40 \pm 2^\circ\text{C}$ 温度下, 将电容器加额定直流电压 1hrs .
X7R/X5R/X7T/ X6S	外观无明显可见损伤 容量变化在±12.5%以内 DF 为初始值的 2 倍以下 IR: 大于 $500\text{M}\Omega$ 或 $5\Omega \cdot \text{F}$ (取较小值) No remarkable visual damage $C_p \text{ change} \leq \pm 12.5\%$ DF: Not more than 2 times of initial value $R * C \geq 500\text{M}\Omega$ or $5\Omega \cdot \text{F}$, whichever is smaller	去掉电压, 将电容器在室温下放置 $48 \pm 4\text{hrs}$ 测量初始电容值。 Test temperature: $40 \pm 2^\circ\text{C}$ Humidity: 90~95% RH Voltage: 100% of the rated voltage Testing time: $500 \pm 12\text{hrs}$
Y5V	外观无明显可见损伤 容量变化在±30%以内 DF 为初始值的 1.5 倍以下 IR: 大于 $500\text{M}\Omega$ 或 $5\Omega \cdot \text{F}$ (取较小值) No remarkable visual damage $C_p \text{ change} \leq \pm 30\%$ DF: Not more than 1.5 times of initial value $R * C \geq 500\text{M}\Omega$ or $5\Omega \cdot \text{F}$, whichever is smaller	Measurement to be made after being kept at room temperature for $24 \pm 2\text{hrs}$ (COG) or $48 \pm 4\text{hrs}$ (X7R, X5R, Y5V, X7T, X6S) *Apply the rated DC voltage for 1 hour at $40 \pm 2^\circ\text{C}$. Remove and let sit for $48 \pm 4\text{hrs}$ at room temperature. Perform the initial measurement.

备注: 该项可靠性试验仅适用于常规产品, 不适用于中高压产品。

产品标准书	编 号 Document No.
SPECIFICATIONFOR APPROVAL	DRAAW108J/0-2021

6.16 耐久性 Life Test

类型 Dielectrics	技术要求 Specification	测试条件 Testing Condition
COG	<p>外观无明显可见损伤 容量变化在$\pm 3\%$或$\pm 0.3\text{pF}$ (取较大值) 以内 容量在 30pF 以上, $Q \geq 350$ 容量在 10pF 以上且 小于 30 pF , $Q \geq 275 + (2.5 * Cp)$ 容量小于 10pF,$Q \geq 200 + 10 * Cp$ IR: 大于 $1000\text{M}\Omega$ 或 $5\Omega \cdot \text{F}$(取较小值) No remarkable visual damage $Cp \text{ change} \leq \pm 3\% \text{ or } \pm 0.3\text{pF}$, whichever is larger. $Q \geq 350$ ($Cp \geq 30 \text{ pF}$) $Q \geq 275 + (2.5 * Cp)$ ($10 \text{ pF} \leq Cp < 30 \text{ pF}$) $Q \geq 200 + 10 * Cp$ ($Cp < 10 \text{ pF}$) $R * C \geq 1000\text{M}\Omega$ or $5\Omega \cdot \text{F}$, whichever is smaller</p>	<p>测试温度: 上限类别温度$\pm 3^\circ\text{C}$ 电压: $U_R < 100\text{V}$ 1.5 倍额定电压 测试时间: 1000 小时</p> <p>在室温下放置 24 ± 2 (COG) 或 48 ± 4 (X7R、X5R、Y5V、X7T、X6S) 小时以后测量</p> <p>*高介电常数电容器的初始值测量 在上限类别温度$\pm 3^\circ\text{C}$, 将电容器加 1.5 倍额定直流电压 1 小时 去掉电压, 将电容器在室温下放置 48 ± 4 hrs 测量初始电容值</p> <p>Test temperature: Max. Operating Temp. $\pm 3^\circ\text{C}$ Voltage: $U_R < 100\text{V}$ 150% of the rated voltage Testing time: 1000 hrs</p>
X7R/X5R/X7T/ X6S	<p>外观无明显可见损伤 容量变化在$\pm 12.5\%$以内 DF 为初始值的 2 倍以下 IR: 大于 $1000\text{M}\Omega$ 或 $5\Omega \cdot \text{F}$(取较小值) No remarkable visual damage $Cp \text{ change} \leq \pm 12.5\%$ DF: Not more than 2 times of initial value $R * C \geq 1000\text{M}\Omega$ or $5\Omega \cdot \text{F}$, whichever is smaller</p>	<p>Measurement to be made after being kept at room temperature for 24 ± 2 hrs (COG) or 48 ± 4 hrs (X7R, X5R, Y5V, X7T, X6S)</p> <p>*Initial measurement for high dielectric constant type Apply 150% of the rated DC voltage for one hour at the maximum operating temperature $\pm 3^\circ\text{C}$. Remove and let sit for 48 ± 4 hrs at room temperature. Perform the initial measurement</p>
Y5V	<p>外观无明显可见损伤 容量变化在$\pm 30\%$以内 DF 为初始值的 1.5 倍以下 IR: 大于 $1000\text{M}\Omega$ 或 $5\Omega \cdot \text{F}$(取较小值) No remarkable visual damage $Cp \text{ change} \leq \pm 30\%$ DF: Not more than 1.5 times of initial value $R * C \geq 1000\text{M}\Omega$ or $5\Omega \cdot \text{F}$, whichever is smaller</p>	

备注：该项可靠性试验仅适用于常规产品，不适用于中高压产品。

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

7. 产品包装 Packing


7.1 袋式散装 Bulk Packing

10000 个/袋或按客户要求。Standard packing 10Kpcs/bag; others are according to customer request.

7.2 编带式包装 Tape Packing

规格 Type	尺寸 Size (mm)			编带数量(个/盘 pcs/reel)	
	长度 L	宽度 W	厚度 T	纸带 Paper Tape	塑料带 Plastic Tape
0201	0.6	0.3	0.3	15,000	N/A
0402	1.0	0.5	0.5	10,000	N/A
0603	1.6	0.8	0.8	4,000	N/A
0805	2.0	1.25	≤0.85	4,000	N/A
			>0.85	N/A	2,000 (或 3,000)
1206	3.2	1.6	≤0.85	4,000	N/A
			>0.85	N/A	2,000 (或 3,000)
1210	3.2	2.5	≤1.25	N/A	2,000
			>1.25	N/A	2,000

7.2.1 纸带尺寸 Dimensions of Packing Paper

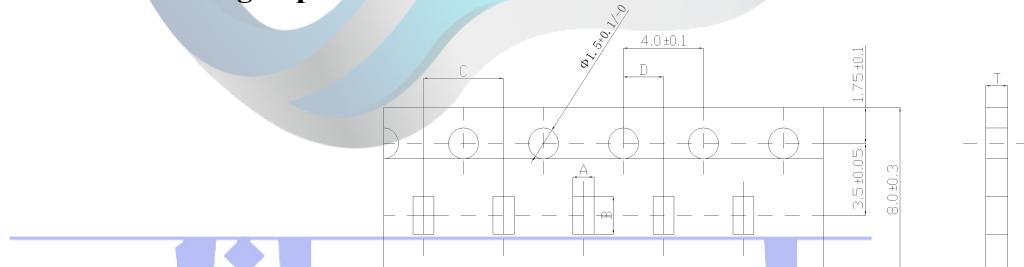

Type	A	B	C	D	T
0201	0.36±0.03	0.67±0.03	2.0±0.10	2.0±0.05	0.42max
0402	0.65±0.10	1.15±0.10	2.0±0.05	2.0±0.05	0.8max
0603	1.05±0.10	1.85±0.10	4.0±0.10	2.0±0.10	1.1max
0805	1.55±0.15	2.3±0.15	4.0±0.10	2.0±0.10	1.1max
1206	1.95±0.15	3.5±0.15	4.0±0.10	2.0±0.10	1.1max

(单位 unit:毫米 mm)

PARTSAZAN Co.

@PARTSAZAN_LED

电话(Tel) : 86-768-6855949 , 685923


E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928 , 68559214


Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021


7.2.2 塑料带尺寸 Dimensions of Embossed Packing

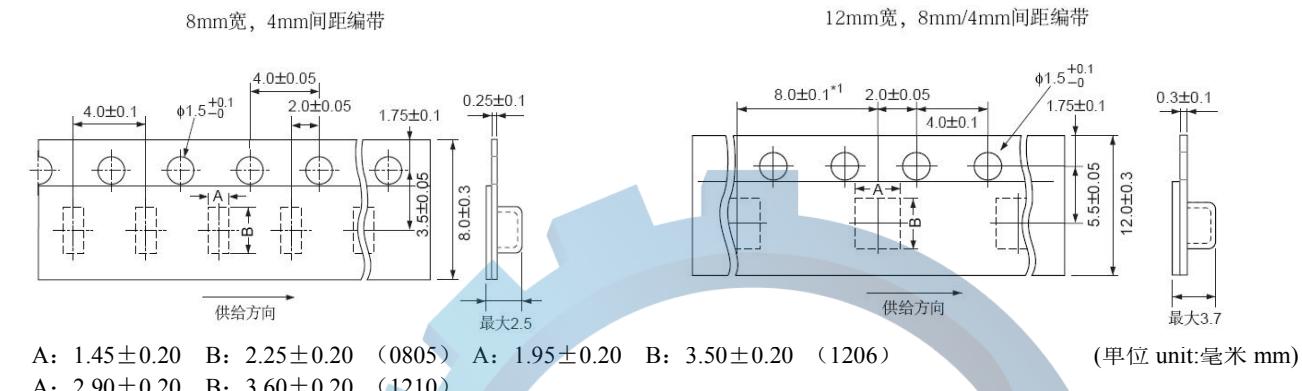

7.2.3 编带盘尺寸 Dimensions of Reel

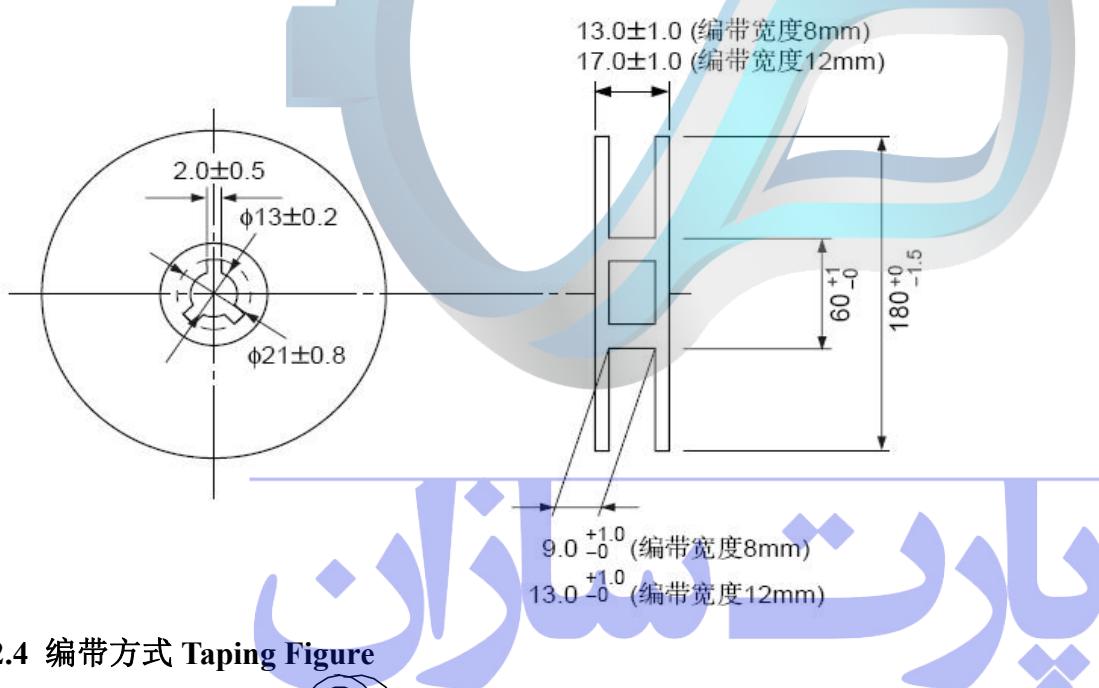

7.2.4 编带方式 Taping Figure

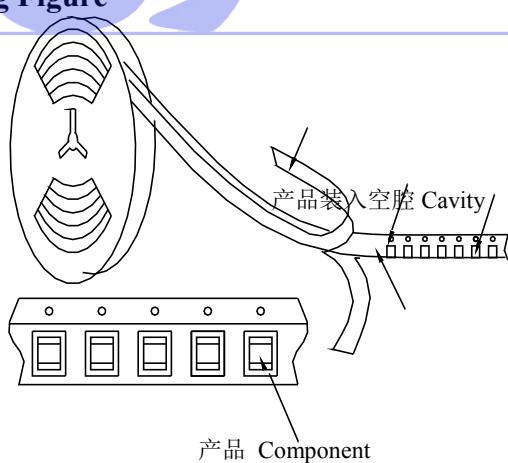
PARTSAZAN Co.
@PARTSAZAN_LED
02166732484

电话(Tel): 86-768-6855949, 685923


 E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214

 Website: <http://www.cctc.cc/>


产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

空白部分 Empty section 产品装入部分 Chip insertion section 空白部分 Empty section

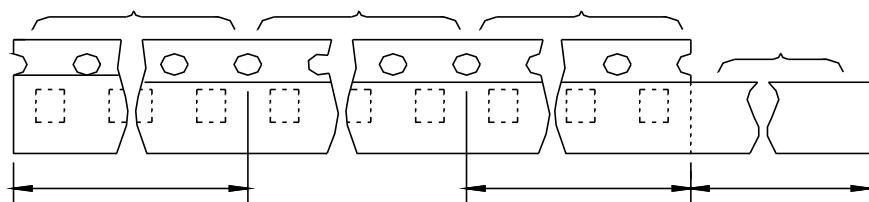


7.2.5 编带方法 Taping Method

- ① 包装电容器的编带是顺时针卷绕的，由上往下的方向拉出编带时，传送孔处于编带的右侧。
 - ② 在编带的前端，至少留出 5 个间距的引出带。
 - ③ 在编带时，必须按下图留出引带部分或空白部分。
 - ④ 在盘带的安装中的产品装错的数量每盘必须小于表示数量的 0.1% 或 1 个为限，不连续发生错误。
 - ⑤ 上胶带和下胶带不应超出编带的边缘，不能挡住传送孔。
 - ⑥ 传送孔的累计误差为 10 个间距：±0.3 毫米以内。
 - ⑦ 上胶带的剥离力矩应在 0.1 至 0.6 牛顿以内，其方向如下图所示。
- (1) Tapes for capacitors are wound clockwise. The sprocket holes are to the right as the tape is pulled toward the user.
 (2) The top tape and base tape are not attached at the end of the tape for a minimum of 5 pitches.
 (3) Part of the leader and part of the empty tape shall be attached to the end of the tape as follows.
 (4) Missing capacitors number within 0.1% of the number per reel or 1pc, whichever is greater, and are not continuous.
 (5) The top tape and bottom tape shall not protrude beyond the edges of the tape and shall not cover sprocket holes.
 (6) Cumulative tolerance of sprocket holes, 10 pitches: ±0.3mm.
 (7) Peeling off force: 0.1 to 0.6N in the direction shown down.

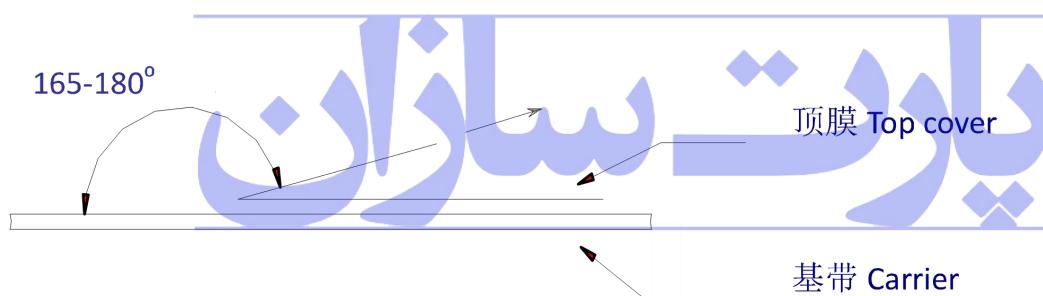

产品标准书 SPECIFICATION FOR APPROVAL	编 号 Document No. DRAAW108J/0-2021
---	--

7.2.6 产品标签 Reel Label

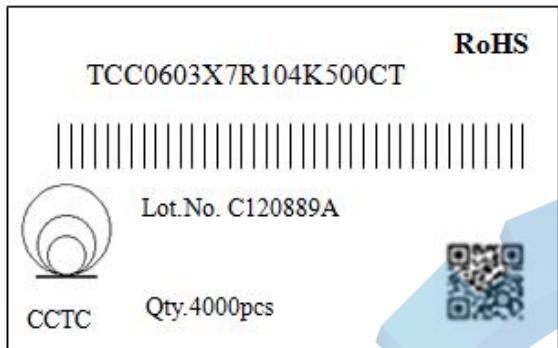

标签内容 The Contents of Label

(1) TCC 0603 X7R 104 K 500 C T
 ① ② ③ ④ ⑤ ⑥ ⑦ ⑧

- ①陶瓷电容器代号 Code of Ceramic Capacitor
- ②尺寸 chip size, ③温度特性 dielectrics, ④容量 capacitance, ⑤容量容差 tolerance,
- ⑥额定电压 rated voltage, ⑦厚度 thickness, ⑧包装 packing

(2) 产品批号 Lot. No.: C120889A

(3) 数量 Qty: 4000pcs

(4) RoHS:GREEN PARTS 绿色物料

7.2.7 外包装 Package

7.2.7.1 包装箱 Carton

7.2.7.1.1 包装箱尺寸 Carton Size

L	W	H
41.0cm	38.5cm	20.2cm

7.2.7.1.2 数量: 240Kpcs /箱 The Quantity: 240Kpcs /one carton

1 内包装盒=40,000PCS 1 INNER BOX=40,000PCS

1 包装箱 =40,000PCS × 6 包装盒=240,000PCS 1 CARTON=40,000PCS × 6 INNER BOX =240,000PCS

RoHS 标识(根据客户要求张贴) according to customer request

**PARTSAZAN Co.
 @PARTSAZAN_LED**

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214

Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

7.2.7.2 内包装盒 Inner Box

7.2.7.2.1 包装盒尺寸 Size



L	W	H
18.5cm	6.5cm	19cm

7.2.7.2.2 数量: 40Kpcs /盒

1 盘=4000PCS 1 REEL=4,000PCS

1 包装盒=4,000PCS × 10 盒 =40,000PCS

1 INNER BOX=4,000PCS × 10REEL =40,000PCS

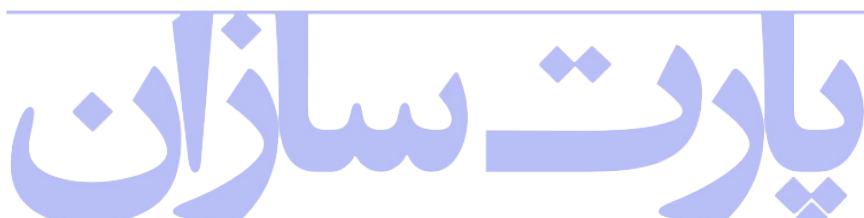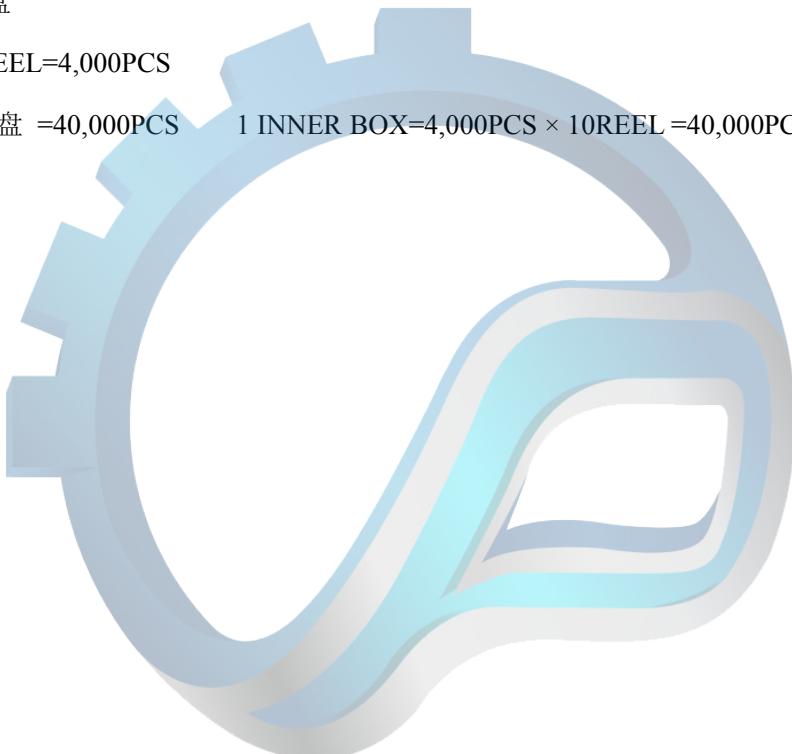

PARTSAZAN Co.

@PARTSAZAN_LED

02166732484

传真(Fax): (768) 6855928, 6855921

网站(Website): <http://www.cctc.cc>

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

8.MLCC 使用注意事项 Precautions on the use of MLCC

8.1 电路板设计 PCB Design

8.1.1 电路板图案设计 Design of Land-patterns

下面图和表格给出了部分推荐的设计图案，可以防止安装时焊锡量过多。

同时也给出了不正确的图案。

The following diagrams and tables show some examples recommended patterns to prevent excessive solder amounts (larger fillets which above the component end terminations)

Examples of improper pattern designs are also shown.


电路板设计推荐图案尺寸：

Recommended land dimensions for a typical chip capacitor land patterns for PCBs

波峰焊接时推荐设计的尺寸 (单位: mm):

Recommended land dimensions for wave-soldering (unit: mm)

规格 SIZE		0603	0805	1206
尺寸	L	1.6	2.0	3.2
	W	0.8	1.25	1.6
A	0.8~1.0	1.0~1.4	1.8~2.5	
B	0.5~0.8	0.8~1.5	0.8~1.7	
C	0.6~0.8	0.9~1.2	1.2~1.6	

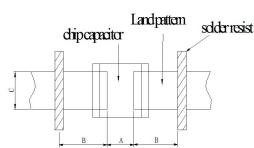

再流焊接时推荐设计的尺寸 (单位: mm)

Recommended land dimensions for reflow-soldering (unit: mm)

规格 SIZE		0201	0402	0603	0805	1206	1210
尺寸	L	0.6	1.0	1.6	2.00	3.2	3.2
	W	0.3	0.5	0.8	1.25	1.6	2.5
A	0.20~0.25	0.35~0.45	0.6~0.8	0.8~1.2	1.8~2.5	1.8~2.5	
B	0.20~0.30	0.40~0.50	0.6~0.8	0.8~1.2	1.0~1.5	1.0~1.5	
C	0.25~0.35	0.45~0.55	0.6~0.8	0.9~1.6	1.2~2.0	1.6~3.2	

过量的焊锡会影响产品抵抗机械应力的能力，因此在设计图案时应引起注意。

Excess solder can affect the ability of chips to withstand mechanical stresses. Therefore, please take proper precautions when designing land-patterns.

在应用中一些焊接好与坏的情况：

Examples of good and bad solder application

**PARTSAZAN Co.
@PARTSAZAN_LED**







电话(Tel) : 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928, 68559214

Website: <http://www.cctc.cc/>



产品标准书 SPECIFICATIONFOR APPROVAL	编 号 Document No.
	DRAAW108J/0-2021

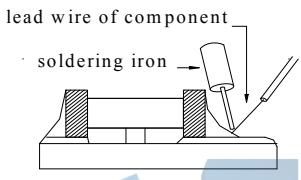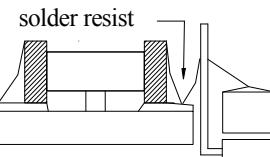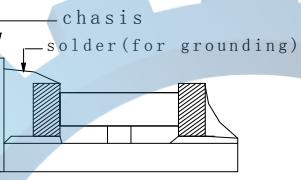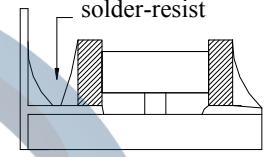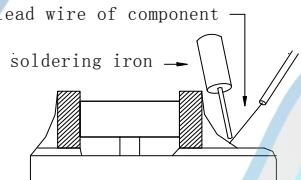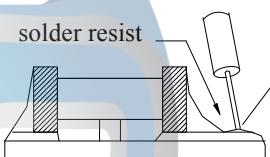项目 Item	不推荐结构 Not recommended	推荐结构 Recommended
片状元件和带引线的元件的混合焊接 Mixed mounting of SMD and leaded component		
靠近底座的焊接 Component placement close to the chassis		
在片状元件附近 带引线元件的焊接 Hand-soldering of leaded components near mounted components		

8.1.2 图案结构 Pattern configurations

下面是电容器安装好与坏的例子。选择贴装位置，应尽可能减小电路板在弯曲时受到的机械应力。

The following are examples of good and bad capacitor layout, SMD capacitors should be located to minimize any possible mechanical stresses from board warp or deflection.

	不推荐结构 Not recommended	推荐结构 Recommended
电路板弯曲 Deflection of the board		

对于电路板分拨的电容器，在分拨时受到的机械应力大小与电容器的安装有关。下面推荐了一些好的设计。To layout the capacitors for the breakaway PC board, it should be noted that the amount of mechanical stresses given depending on capacitor layout. The example below shows recommendations for better design.


**PARTSAZAN Co.
@PARTSAZAN_LED**

电话(Tel)：86-768-6855949, 685923
 E-mail: market@china-threecircle.com

传真(Fax)：(768) 6855928, 68559214

Website: <http://www.cctc.cc/>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

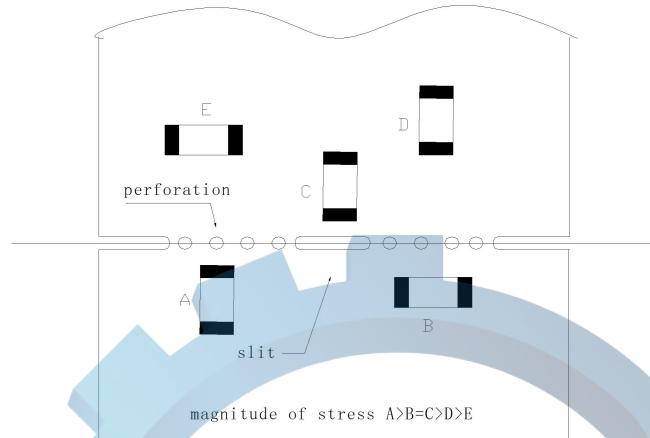





在沿着分拨线分拨电路板时，对产品施加的机械应力与使用的方法关系很大。分折电路板时片状元件受到的疲劳按照如下顺序增大：分折、剪切、V型槽、穿孔。因此，贴装时应该考虑电路板的分拨过程。

When breaking PC boards along their perforations, the amount of mechanical stress on the capacitors can vary according to the method used. The following methods are listed in order from least stressful to most stressful: push-back, silt, -grooving, and perforation. Thus, any ideal SMD capacitor layout must also consider the PCB splitting procedure.

8.2 自动贴装注意事项 Considerations for automatic placement

贴装机的调整 Adjustment of mounting machine

- ①. 产品在电路板贴装时，不应该受到过大的冲击。
 - ②. 必须定期对吸头和定位爪进行检查、维修和更换
- ①. Excessive impact load should not be imposed on the capacitors when mounting the PC boards.
 - ②. The maintenance and inspection of the mounters should be conducted periodically.

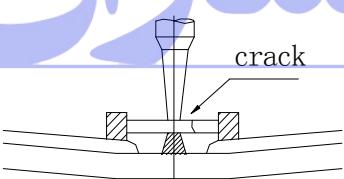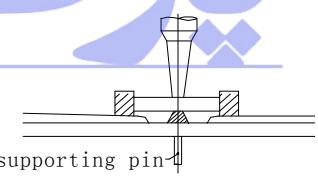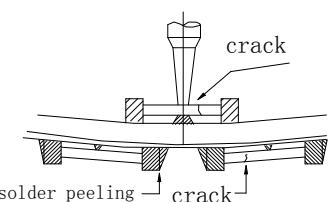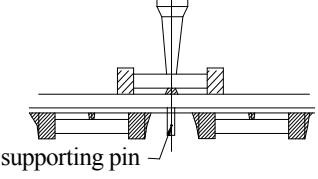	不推荐结构 Not recommended	推荐结构 Recommended
单面贴装 Single-sided mounting		
双面贴装 Double-sided mounting		

**PARTSAZAN Co.
@PARTSAZAN_LED**

电话(Tel) : 86-768-6855949, 685923

 E-mail: market@china-threecircle.com

传真(Fax) : (768) 6855928, 6855921

 Website: <http://www.cctc.cc>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021


8.3 推荐焊接曲线 Recommended soldering profile

8.3.1 说明: ① 产品推荐使用回流焊接工艺; ② 大尺寸产品适用于回流焊接工艺

Re: ①flow Soldering is recommended; ②flow soldering is suitable for bigger size MLCCs

8.3.2 锡铅焊接曲线 Recommended Sn&Pb soldering profile


回流焊 Reflow soldering

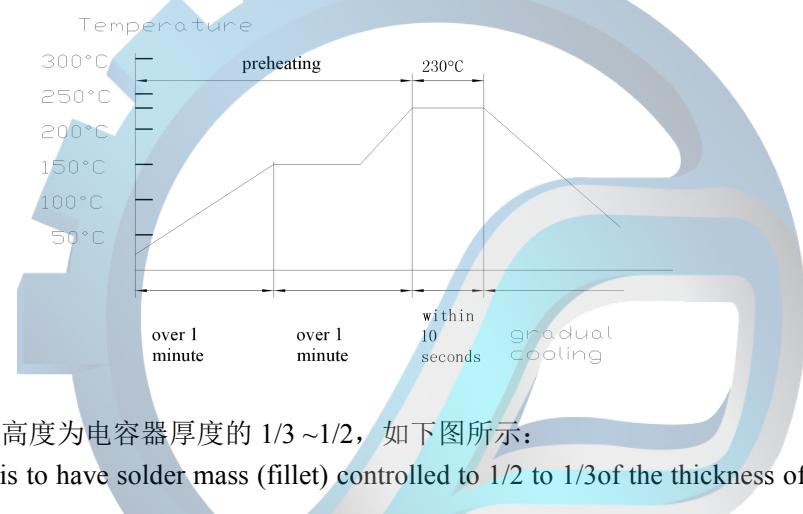

注意 Caution

① 理想状况的焊锡高度为电容器厚度的 1/3 ~ 1/2, 如下图所示:

①.The ideal condition is to have solder mass (fillet) controlled to 1/2 to 1/3 of the thickness of the capacitor, as shown below:

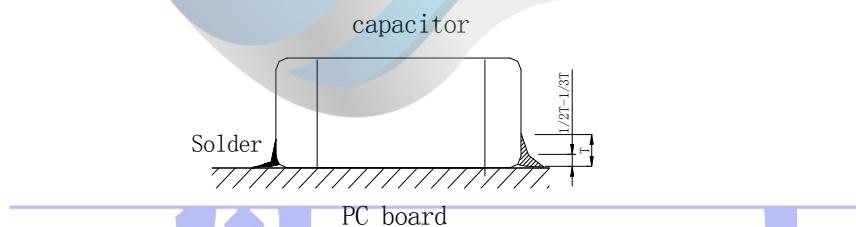


②. 过长的焊接时间会影响端头的可焊性, 焊接时间尽可能保持与推荐时间一致。

②. Because excessive dwell times can detrimentally affect solderability, soldering duration should be kept as close to recommended times as possible.

波峰焊

Wave solder profile

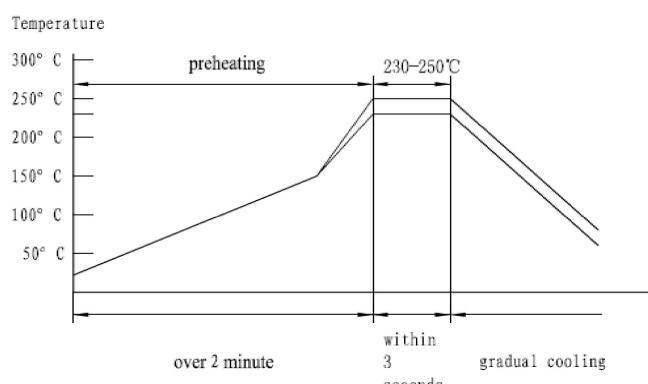

PARTSAZAN Co.

@PARTSAZAN_LED

02166732484

(768) 6855928, 6855921

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 6855921

Website: <http://www.cctc.cc>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

注意 Caution


- ①. 确保电容器充分预热。
 - ②. 产品预热和焊接温度差不超过 100~130°C。
 - ③. 焊接后尽可能慢速冷却。
- ①. Make sure the capacitors are preheated sufficiently.
 ②. The temperature difference between the capacitor and melted solder should not be greater than 100 to 130°C.
 ③. Cooling after soldering should be gradual as possible.

手工焊接 Hand soldering
条件:

预热	烙铁头温度	烙铁功率	烙铁头直径	焊接时间	锡膏量	限制条件
Δ≤130°C	最高350°C	最大20W	建议1mm	最长5s	≤1/2芯片厚度	请勿使用烙铁头直接接触陶瓷原件

注意 Caution

- ①. 用尖端最大直径 1.0mm 功率 20W 的焊接烙铁。
 - ②. 焊接烙铁不要直接接触产品。
- ①. Use a 20w soldering iron with a maximum tip diameter of 1.0mm.
 ②. The soldering iron should not directly touch the capacitor.

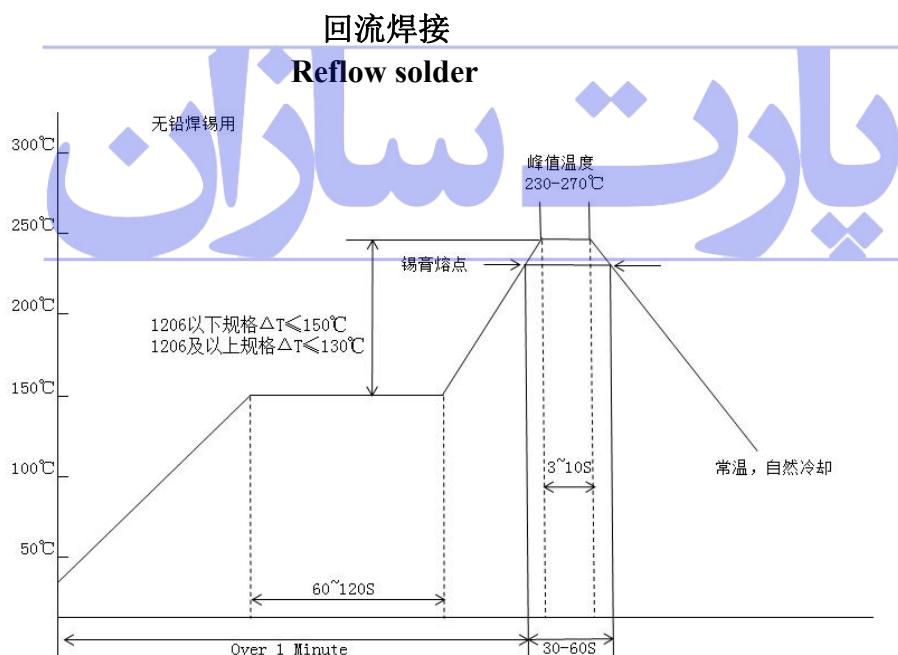
8.3.3 无铅焊接曲线 Recommended Pb-Free soldering profile

PARTSAZAN Co.
@PARTSAZAN_LED

 电话(Tel) : 86-768-6855949, 685923
 E-mail: market@china-threecircle.com

 传真(Fax) : (768) 6855928, 6855921
 Website: <http://www.cctc.cc>

产品标准书	编 号 Document No.
SPECIFICATION FOR APPROVAL	DRAAW108J/0-2021

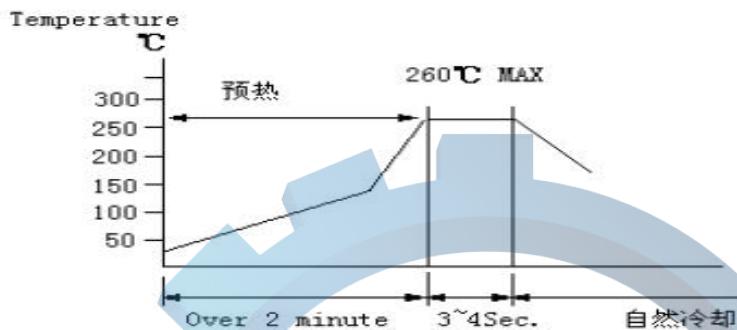波峰焊接
Wave solder profile



8.4 分拨电路板 Handling

Breakaway PC boards (splitting along perforations)

- (1). 在电容器或其它贴装后，必须注意因电路板弯曲或变形带来的应力。
- (2). 分拨电路板时必须使用专用的夹具，不可以用手拔断。
- (1). When splitting the PC board after mounting capacitors and other components, care is required so as not to give any stresses of deflection or twisting to the board.
- (2). Board separation should not be done manually, but by using the appropriate devices.

8.5 保存 Storage

- (1). 在下列环境中保存产品：温度 5~40°C；湿度 ≤70% RH
 - (2). 产品自生产之日起保存期为一年，产品使用之前请勿拆开编带。
 - (3). 编带拆开后，产品应在三个月内使用。
 - (4). 高介电常数电容器 (X7R,X5R,Y5V、X7T、X6S) 的容值随时间会逐渐减小，所以在电路设计时应充分考虑这一现象。容值减小的电容器在 150°C 热处理 1 小时后容值会恢复到初始值。
- (1). Keep the storage environment conditions as following: Temperature: 5~40°C; Humidity: ≤70% RH
 - (2). Don't open the tape until the parts are to be used, and store them within one year since the date printed on the reel.
 - (3). Use the chips within 3 months after the tape is opened.
 - (4). The capacitance value of high dielectric constant capacitors (X7R,X5R,Y5V、X7T、X6S) will gradually decrease with the passage of time, so this should be taken into consideration in the circuit design. If such a capacitance reduction occurs, a heat treatment of 150°C for 1 hour will return the capacitance to its initial level.

PARTSAZAN Co.
@PARTSAZAN_LED

电话(Tel): 86-768-6855949, 685923

E-mail: market@china-threecircle.com

传真(Fax): (768) 6855928, 68559214

Website: <http://www.cctc.cc/>